

Recent Developments in Material Testing for Characterization of Materials (Deformation and Failure) for LS-DYNA Materials Models

Amos Gilat, and Jeremy D. Seidt

Ohio State University, Department of Mechanical Engineering

201 W. 19th Ave., Columbus, OH, 43210

1 Abstract

Several new testing methods that have been recently developed for mechanical characterization (deformation and failure) of materials are presented. The data from these tests is used for the development and calibration of material models (constitutive relations) in LS-DYNA. The first method involves the use of Digital Image Correlation (DIC) in tests that are used for generating data needed for the MAT224 model. In these tests specimens with different geometries are loaded and DIC measurements are used for determining the equivalent failure strain as a function of stress triaxiality and Lode parameter. The second testing method is a shear test for sheet metals. The experiment is done by using a flat notched specimen in a tensile apparatus. The shear strain is measured by using DIC within and on the boundary of the notch. The third development is a dynamic punch test in which the deformation of the specimen is measured continuously with 3-D DIC. The fourth is a high strain rate tensile testing technique for Kevlar cloth and Kevlar yarn in a tensile Split Hopkinson Bar (SHB) apparatus. The Kevlar cloth/yarn is attached by specially designed adaptors that keep the impedance constant. In addition to the traditional method of determining the specimen's strain from the recorded waves in the bars the strain is also measured with DIC. The fifth development is an apparatus for testing at intermediate strain rates in compression. In this apparatus the specimen can be deformed at strain rates ranging from 20 s⁻¹ to 200 s⁻¹. The apparatus is a combination of hydraulic actuator and a long (40 m) transmitter bar. The stress in the specimen is determined from the stress wave and the strain and strain rate is determined by using DIC. The results show very clean (no ringing) stress strain curves.

2 Background

Numerical simulation of the response of materials under loads has reached a level of maturity at which it can be used with confidence for design purposes. Numerical codes like LS-DYNA include many material models for deformation and failure (constitutive relations) that can be selected for specific applications. The various models require input parameters that are specific to the material that is being simulated. The accuracy of the simulations depends on the values of the input parameters which are determined from experimental data.

The focus of the present paper is on several new testing configurations and techniques that have been developed recently for the purpose of providing accurate data for determining the parameters in material models for deformation and failure.

3 Testing for MAT224 Input

MAT224 is a relatively new deformation and failure model in LS-DYNA. The input requires stress strain curves from tests at different strain rates and temperatures and values of equivalent failure strain at various state of stress (various combinations of stress triaxiality and Lode parameter). The failure data is obtained from plane stress tension tests of smooth specimens, tension tests of notched flat and notched round specimens with different notch sizes, plane strain tension experiments with smooth and notched specimens with different notch sizes, and biaxial tension-torsion and

compression-torsion tests and punch tests. Digital Image Correlation (DIC) is used in all the tests for a direct measurement of the deformation (full field) on the surface of the specimens. The DIC data together with numerical simulation of the experiments is used for determining the state of stress (triaxiality and Lode parameter) and deformation in the specimens throughout the test and at the instant of fracture. For example, the axial and transverse strains measured with DIC in one instant during a tension test of a notched round specimen are shown in Figures 1 and 2.

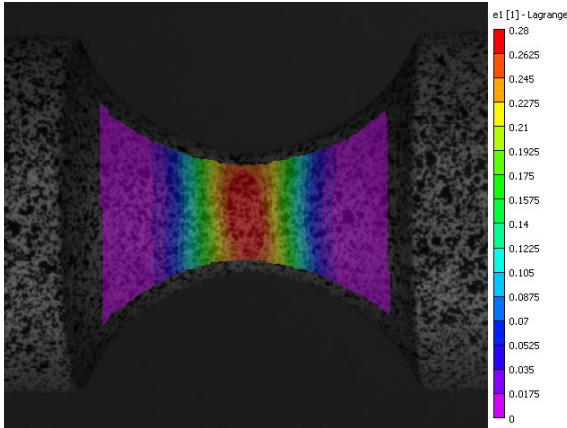


Fig. 1: Axial DIC strains in tension test of notched specimen.

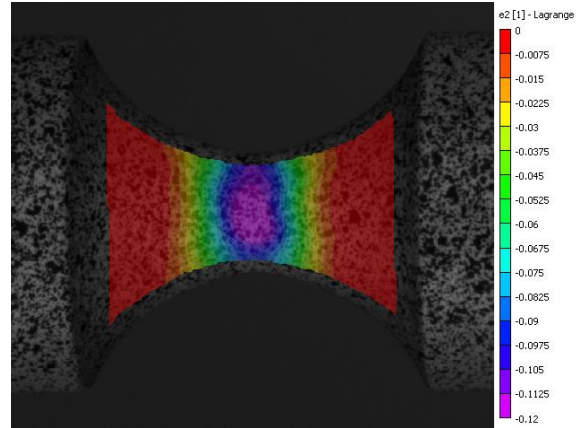


Fig. 2: Transverse DIC strains in tension test of notched specimen.

4 Shear Test for Sheet Metal

Simulation of many applications in the automotive and aerospace industries requires knowledge of the shear properties of sheet metals. Shear properties are ideally obtained from a torsion test of a thin-walled tube where the gage section is under a state of simple shear. Since tubes cannot be machined from sheet metal other methods need to be used. A new testing configuration for shear of specimen made of sheet metal is presented. The specimen, shown in Figure 3 is loaded in tension by pulling on the end tabs. The gage section, which is the notch in the center, is under a stress state of nearly pure shear. The average shear stress in the gage section is determined by dividing the force by the area in the gage section that is being sheared. The shear strain is determined by measuring the deformation with DIC directly in the gage section. Figure 4 shows processed data from one DIC frame. The figure shows a state of almost pure shear within the notch. Figure 5 shows a shear stress strain curve from a test with specimen made of 2024-T351 aluminum. The test can also be conducted at high strain rate by using a tensile split Hopkinson bar apparatus.

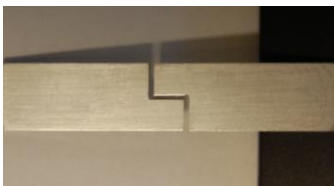


Fig. 3: Sheet metal shear specimen.

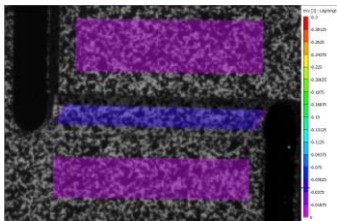


Fig. 4: Shear strain measured with DIC.

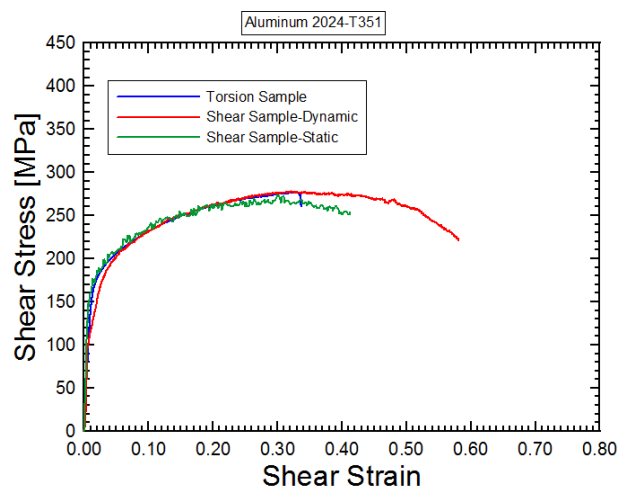


Fig. 5: Shear stress strain curves for 2024 aluminum.

5 Dynamic Punch Test

A dynamic punch test is conducted by placing a punch that has a rounded (or flat) nose on the end face of the incident bar of a compression split Hopkinson bar apparatus, and a thin round, flat, specimen plate restricted around the circumference on the end face of the transmitter bar, Figure 6. A compression wave that is generated in the incident bar causes the punch to penetrate the plate. The force applied by the punch is measured by the wave in the transmitter bar. The relative motion between the punch and the specimen mount is measured during the test using Digital Image Correlation (DIC). The relative displacement between the punch and the specimen can be unrestricted or restricted to a predesigned magnitude. In this way a series of tests can be done where the punching process is stopped at different stages and the specimens are recovered and examined. Figure 7 shows results from tests on specimens made of 2024-T351 aluminum. Figure 8 shows the recorded force versus displacement for each of the tests that are shown in Figure 7. The punch test can also be done such that the deformation of the back of the specimen is measured continuously with three-dimensional DIC during the test. Figure 9 shows The results are used for the development and validation of continuum ductile fracture models for high strain rate applications.

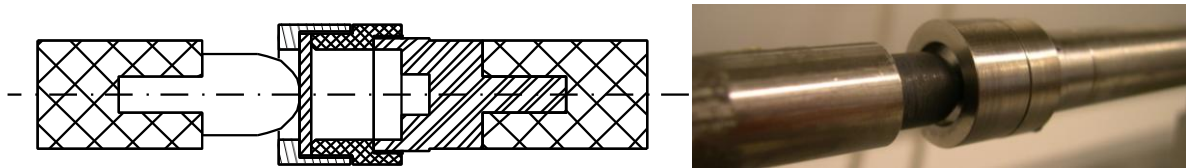


Fig. 6: Dynamic punch test.

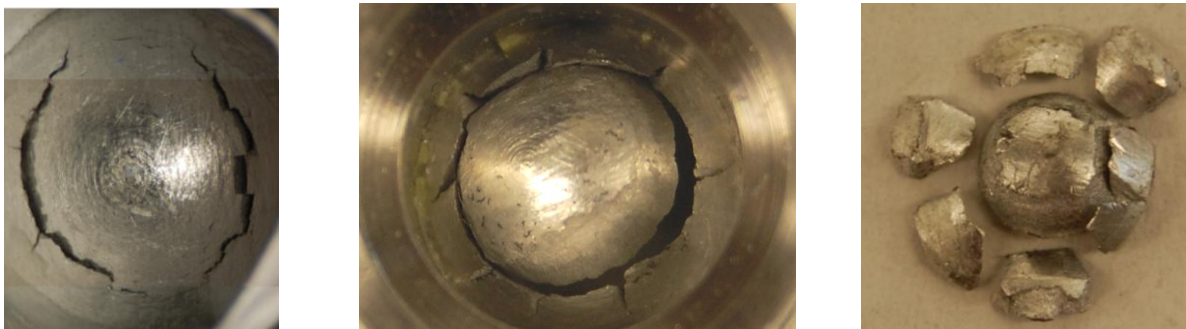


Fig. 7: Recovered specimens from dynamic punch test.

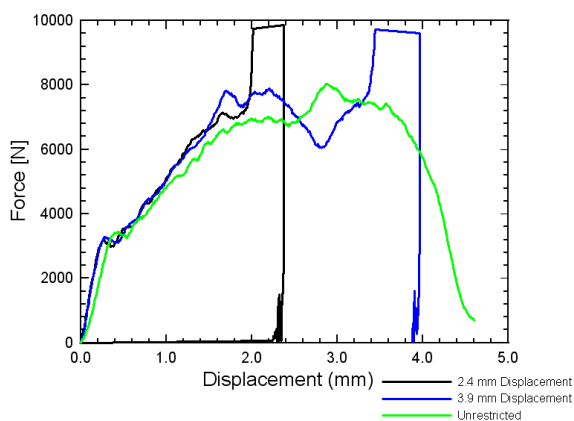


Fig. 8: Force versus displacement records for the tests shown in Figure 7.

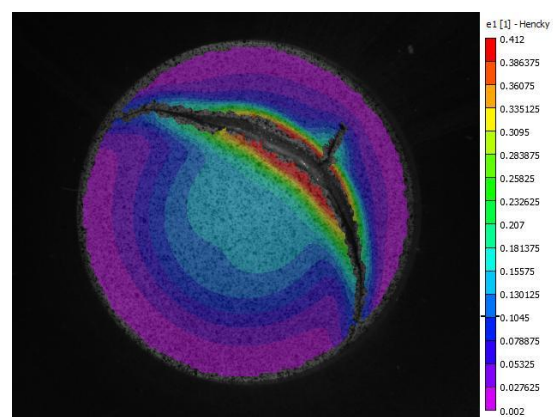


Fig. 9: Strain measured with DIC in a dynamic Punch test.

6 Tensile Testing of Kevlar at High Rate

Testing Kevlar cloth and yarn requires special attention to the mounting, or gripping, of the specimen. At low (quasi-static) strain rates there are no limits on the specimen and mounting fixtures geometries.

Testing these materials with the tensile split Hopkinson bar apparatus requires special attention since the specimen has to be small, has to be attached between the bars while keeping the impedance constant, and the connection has to be strong enough such that the specimen will fracture in the gage section between the bars. Figures 10 and 11 show fractured Kevlar 49 cloth specimen and fractured single yarn specimen following a test.

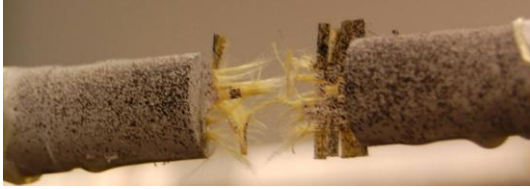


Fig. 10: Kevlar cloth following a tensile SHB test.

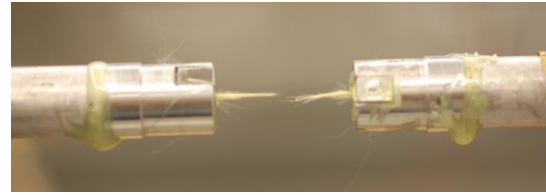


Fig. 11: Kevlar yarn following a tensile SHB test.

The stress and strain in the specimen are determined from the wave in the bar using the standard method. In addition, the strain is determined with DIC directly on the specimen and from measuring the displacements of the adaptors. Figure 12 shows DIC data (displacements) from one frame during the test, and Fig. 13 shows stress strain curves from a test with Kevlar 49 cloth.

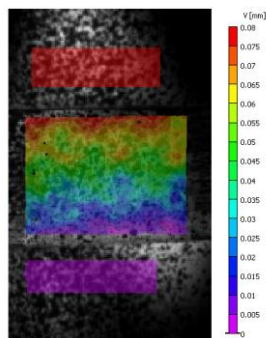


Fig. 12: DIC data from a SHB test on Kevlar cloth.

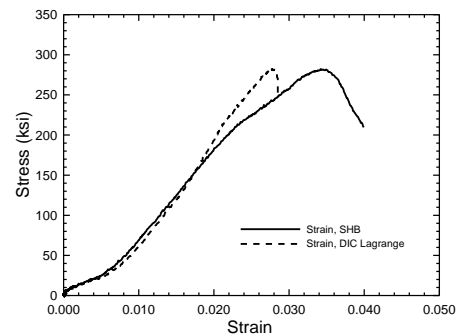


Fig. 13: Tensile stress strain curve for Kevlar cloth.

7 Intermediate Strain Rate Test

A new technique for testing in compression at intermediate strain rates ranging from about 20 s^{-1} to 200 s^{-1} is presented. The technique is a hybrid of a compression SHB and a hydraulic machine. A specimen (short, small diameter cylinder) that is placed on the face of the cross-section of a long bar is loaded by a hydraulic actuator, Fig. 14. As the specimen is loaded, a compression wave propagates to the end of the bar and reflects back. The force in the specimen is measured by strain gages that are placed on the bar and the strain is measured directly on the specimen with DIC. The actual setup is shown in Figs. 15 and 16.

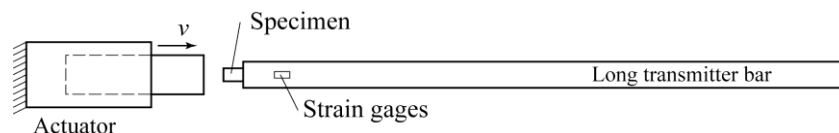


Fig. 14: Schematic of the intermediate strain rate apparatus.



Fig. 15: Intermediate strain rate apparatus.

The bar is more than 40 m long which allows a test duration (until the reflected wave arrives at the strain gages that measure the force) of more than 0.016 s. At a strain rate of 20 s^{-1} it provides enough time for the specimen to deform to a strain of 0.3. Results from a test on a 6061-T6 aluminium specimen are shown in Figs. 17 and 18. Figure 17 shows one DIC frame during the test, and the stress strain curve from the test is shown in Fig.18. The strain rate during this test is approximately 70 s^{-1} .

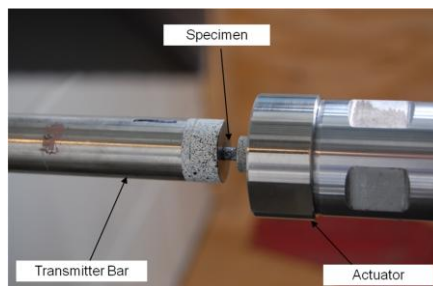


Fig. 16: Intermediate strain rate apparatus.

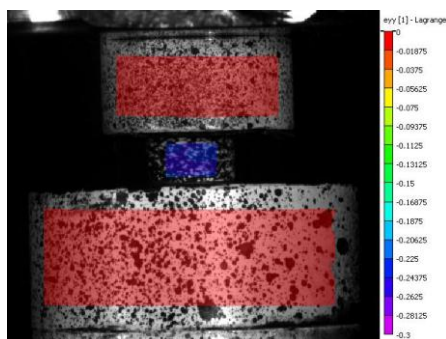


Fig. 17: Axial strain measured with DIC.

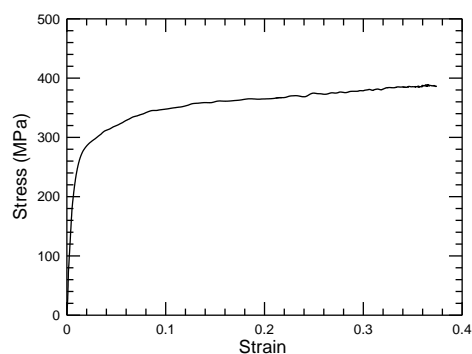


Fig. 18: Stress strain curve for 6061-T6 aluminum.

8 Acknowledgements

The development of the testing techniques for the data needed for MAT224, the tensile testing of Kevlar, the shear test for sheet metal, and the dynamic punch test was supported by the U.S.A. Federal Aviation Administration, Grant No. 2006G004. The shear test with sheet metal was initially developed by Mr. Matti Isakov from Tampere University of Technology, Finland. Additional tests and modifications were done by Mr. Kevin Gardner. The development of the intermediate strain rate test was done by Mr. Thomas Matrka with support from NASA, Grant No. NNX08AB50A